



FABRICATION OF TRANSITION METAL-DOPING TiO₂ COMPOSITE AND ITS PHOTOCATALYTIC DEGRADATION PERFORMANCE TOWARD THE AMMONIA NITROGEN COMPOUNDS IN FARM WASTEWATER


Shengqiang WANG,^a Qijie XU,^{a,*} Yang ZHANG,^a Gaofeng JIN,^a Weiwei HE^b and Ning ZHANG^a

^aCollege of Chemistry-Pharmaceutical Engineering, Huanghuai University, Zhumadian 463000, Henan, China

^bCollege of Advanced Materials and Energy, Xuchang University, Xuchang, 461000, Henan, China

Received January 15, 2020

TiO₂ and transition metal-doping TiO₂ composite, including Cu, Co, Ni, Ag, Au element, were prepared by sol-gel method by using tetrabutyl titanate and different metal salts as raw materials. TiO₂ and its composites were characterized by means of UV-vis, FTIR, and fluorescence spectrometry, etc. Further, photocatalytic degradation properties of TiO₂, Cu/TiO₂, Co/TiO₂, Ni/TiO₂, Ag/TiO₂ and Au/TiO₂ toward ammonia-nitrogen compounds in farm wastewater were studied under simulated sunlight. The results showed that the transition metal-doping TiO₂ composite possessed higher photocatalytic degradation properties than pure TiO₂, among which, the degradation rate of Ag/TiO₂, Au/TiO₂ and Ni/TiO₂ reached to 30.3%, 29.9%, and 26.9%, respectively, and those of Cu/TiO₂ and Co/TiO₂ were 25.0% and 26.3%, respectively. Photocatalytic degradation conditions of ammonia nitrogen compounds were investigated by using Ag/TiO₂ as photocatalyst. It was found that the degradation rate of ammonia nitrogen compounds could reach 37.5% when the initial concentration was 0.07 g/L, the time was 180 min, and the dosage of catalyst was 0.10%. Additionally, in comparison with natural sunlight as the light source, the degradation efficiency of the catalyst was still reaching to 32.6%, which indicated the perfect application prospect in the treatment of farm wastewater.

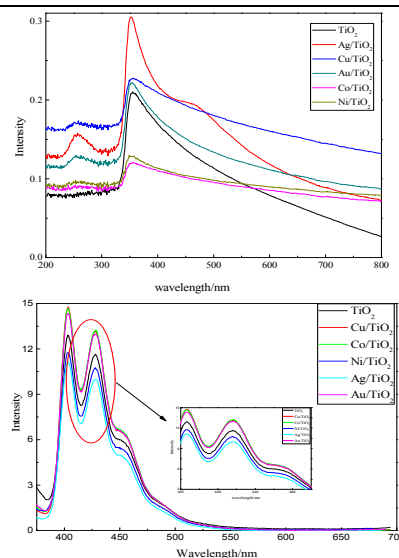

INTRODUCTION

Photocatalytic degradation of organic pollutant based on semiconductors materials as photocatalyst is one of most active and promising research directions due to semiconductors such as TiO₂, ZnO, Ag₃PO₄ are low-cost, stable, nontoxic and environmental friendly.¹⁻⁴ Moreover, the operation condition of photocatalytic degradation toward organic pollutant is high efficient and mild.

Titanium dioxide (TiO₂) possesses perfect photoelectric properties, high chemical stability, low cost and safety toward both humans and the

environment, which is widely applied in many fields as catalyst, coating, plastic, and so on.^{1,5-7} Particularly, TiO₂ as photocatalyst can decompose the organic compound that, recently, becomes popular research directions. However, narrow light response range only to ultraviolet limits the utilization efficiency of actual sunlight. Further, the recombination rate of hole and electron induced electron-hole pairs of TiO₂ photocatalytic system that seriously affects the photocatalytic rate. In order to improve the photocatalytic activity as well as the response into visible-light region, TiO₂ doping with transition metals has been widely

* Corresponding author: qijie001@163.com

investigated.^{8–11} Usually, the metal selective doping is one of the common approaches to enhance the photocatalytic efficiency of the catalyst. A series of titania-metal composites (mainly including noble metals and noble/transition metal ions) have been used in order to increase the efficiency of the photocatalytic process.^{12–15}

Bear these perspectives in mind, the present work pays special attention to synthesize transition metal (Cu, Co, Ni, Ag, and Au) doped TiO₂ composite by hydrothermal method. Then the photocatalytic degradation properties of as-prepared transition metal-doping TiO₂ composite on ammonia nitrogen compounds in farm wastewater are investigated in the simulated sunlight and actual sunlight.

EXPERIMENTAL

1. Chemicals

Tetrabutyl titanate was supplied by Tianchen chemicals, China; Copper (II) sulfate pentahydrate (CuSO₄·5H₂O), cobaltous nitrate hexahydrate (Co(NO₃)₂·6H₂O), nickel chloride hexahydrate (NiCl₂·6H₂O), and silver nitrate (AgNO₃) were obtained from Tianjin Kaitong chemicals Co., Ltd, China; methyl orange was supplied by Sinopharm chemicals reagent Co., Ltd, China. Other reagents are of analytical grade.

2. Preparation of TiO₂ and transition metal doping TiO₂ composite

TiO₂ and transition metal-doping TiO₂ composite were prepared readily by hydrothermal synthesis method.¹¹ Firstly, proper amount of tetrabutyl titanate (2 mL) was added into 20 mL absolute ethanol in a three-neck flask, and then stirred for 30 min under magnetic stirring. Subsequently, the above solution was transferred into hydrothermal reactor of 30 mL under 210 °C for 24 h, then washed by distilled water and absolute ethanol for 3 times, respectively, followed to heat at 80 °C for 24 h thereby affording TiO₂ nanoparticles. Transition metal-doping TiO₂ composite were obtained by using the same synthesis process, the atomic ratio of metal ions (Co²⁺, Ni²⁺, Ag⁺, Au⁺, and Cu²⁺) doping TiO₂ was 2.0 at% and the samples were noted as Co/TiO₂, Ni/TiO₂, Ag/TiO₂, Au/TiO₂, Cu/TiO₂, respectively.

3. Characterization of TiO₂ and transition metal-doping TiO₂ composite

UV-vis absorption spectrum of TiO₂ and transition metal-doping TiO₂ composites were measured over a wavelength range of 200–800 nm with a Cary 100 spectrophotometer. Fluorescence spectrometry (F-2700, Hitachi Company, Japan) was utilized to evaluate the fluorescence properties of TiO₂ and transition metal-doping TiO₂ composites at the range of the wavelength of 220–730 nm. The infrared spectrum of the samples of TiO₂ and transition metal-doping TiO₂ composites were recorded inside KBr pellets on Fourier Transform Infrared Spectrometer (FTIR Avatar360, Nicolet, American).

4. Testing of photocatalytic degradation properties of TiO₂ and transition metal-doping TiO₂ composites toward ammonia nitrogen compounds

The photocatalytic degradation performance of TiO₂ and transition metal-doping TiO₂ composite were measured by monitoring the decomposition of ammonia nitrogen compounds at simulated solar light or nature sunlight. Typically, 0.05 g catalyst and 50 mL farm wastewater were added in a breaker of 100 mL, then the solution was magnetically stirred for 1 h to achieve adsorption saturation before illumination. Following this, the photocatalytic degradation reaction of ammonia nitrogen compounds was carried out via the exposure of simulated solar light or nature sunlight, and the temperature of the reaction system was kept at room temperature by using a constant temperature circulating pump. After a half hour, 2 mL aqueous solution was taken out, centrifuged to test the content of the residual ammonia nitrogen compounds by using UV-vis adsorption spectrum at the main adsorption peak of 420 nm.

RESULTS AND DISCUSSION

1. The photo of standard curve of ammonia nitrogen compounds

The standard curve of ammonia nitrogen compounds was drew according the Chinese standards of water quality (Determination of ammonia nitrogen-Nessler's reagent spectrophotometry, No: HJ 535-2009),¹⁶ as shown in Fig. 1. As-obtained standard curves had perfect linear relationship coefficient (R) of 0.99933 that was consist with relative testing requirements, which could be used for evaluating the content of ammonia nitrogen compounds in farm wastewater.

2. Characterization of TiO₂ and transition metal-doping TiO₂ composite

UV curves of TiO₂ and its composites were shown in Fig. 2. It can be seen that the adsorption peaks were emerged at 350 nm, however, that of TiO₂ obviously decreased with increasing wavelength. Particularly, the adsorption intensity of TiO₂ was lowest in all transition metal-doping TiO₂ composites. The possible reason was owned to the lower electrode potential of transition metal and its ions that was apt to extend the light response range thereby improving the photocatalytic rate. Moreover, the adsorption peaks of Ag/TiO₂ composite appeared two peaks at 350 nm and 450 nm, respectively, that may be concluded from the perfect adsorption of light and led to high photocatalytic degradation rate toward organic pollutants.¹⁷

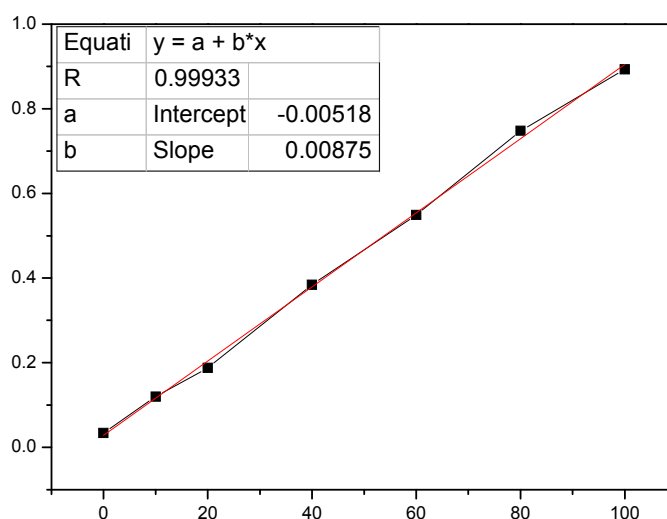
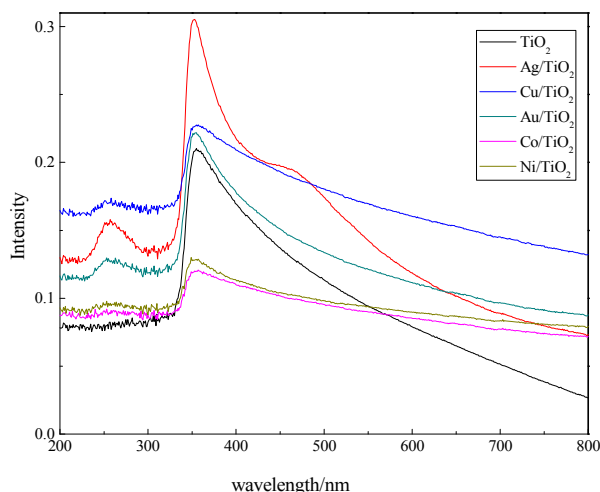
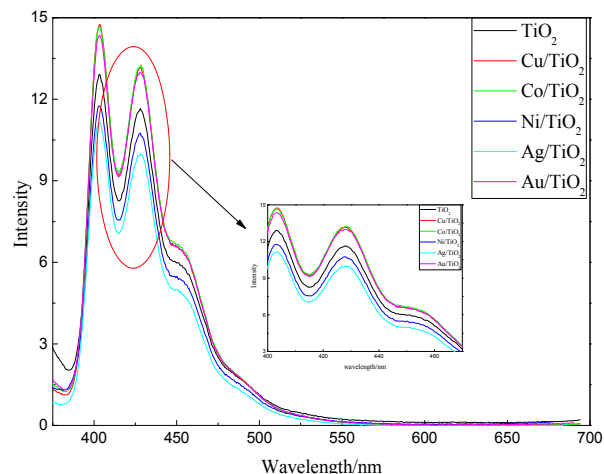


Fig. 1 – Standard curve of ammonia nitrogen compounds.

Fig. 2 – UV curves of TiO₂ and its composites.Fig. 3 – Fluorescence spectra of TiO₂ and its composites.

Another important factor on photocatalytic degradation of organic pollutants is the recombination rate of holes and electrons of photocatalyst. The electron recombination rates of the photocatalysts were characterized by fluorescence spectrometry, the results of which are shown in Fig. 3. Among the emission intensities observed, that of Ag/TiO₂ was the lowest. This result revealed that Ag/TiO₂ had a low electron recombination rate, which enhanced its photocatalytic degradation abilities, which was agreement with experimental result.¹⁸

Transition metal-doping TiO₂ to form based TiO₂ composites affect the crystallization structure of TiO₂. Fig. 4 indicated the FTIR spectra of TiO₂

and its composites, as seen from Fig. 4 that those absorption peaks at 3400 cm⁻¹ belonged to the adsorption peaks of hydroxyl groups ($\cdot\text{OH}$) on the surface of TiO₂. Additionally, that at 2925 cm⁻¹ and 2850 cm⁻¹ represented methyl and methylene ($\cdot\text{CH}_3$ and $\cdot\text{CH}_2$), and that at 1700 cm⁻¹ was the adsorption peak of carbonyl groups (C=O), these peaks were own to residue of the organic chains of tetrabutyl titanate.^{12-14,17} However, the FTIR relative intensity of Ag/TiO₂ and Au/TiO₂ at the rang of 4000-400 nm were stronger than that of TiO₂, the main reason may be the strong adsorption properties of Ag and Au to light, which enhanced the intensity of response light of photocatalyst thereby improving photocatalytic degradation rate.

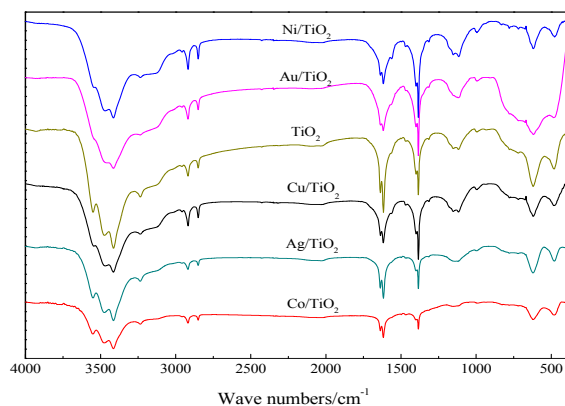


Fig. 4 – FTIR spectra of TiO₂ and its composites.

3. The photocatalytic degradation properties of TiO₂ and its composites on ammonia nitrogen compounds

3.1. The effect of doped transition metal on the photocatalytic degradation properties of TiO₂

The photocatalytic degradation properties of TiO₂, Cu/TiO₂, Co/TiO₂, Ni/TiO₂, Ag/TiO₂, and Au/TiO₂ for ammonia nitrogen compounds were shown in Fig. 5. It can be seen that TiO₂ doped by transition metal displayed better photocatalytic degradation performance toward ammonia nitrogen compounds under simulated sunlight in 120 min, particularly, Ag/TiO₂ and Au/TiO₂ indicated higher degradation rates, as improved 22.1% and 20.7%, respectively, in comparison with that of TiO₂. The main reason owned to the light enhancement effect of Ag and Au that was apt to increase the light response range of TiO₂, thereby improving the photocatalytic degradation rate toward ammonia nitrogen compounds even to other organic pollutants.^{8,9} Among these photocatalyst, Ag/TiO₂ possessed best photocatalytic degradation

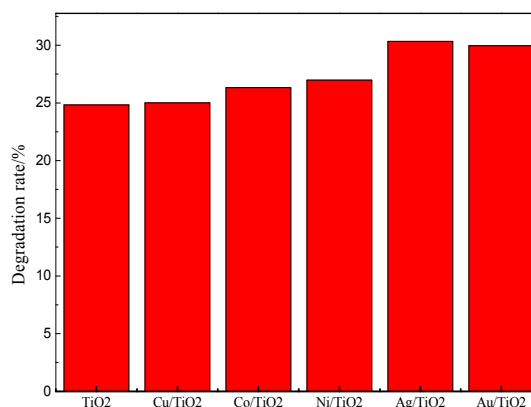


Fig. 5 – Photocatalytic degradation rate of TiO₂ and its composites toward ammonia nitrogen compounds.

properties on ammonia nitrogen compounds, thus, we chose Ag/TiO₂ as photocatalyst to investigated the suitable conditions for photocatalytic degradation of organic pollutants.

3.2. The effect of the initial concentration of ammonia nitrogen compounds on degradation rates

The certain amount of farm wastewater with ammonia nitrogen content of 1.75 g/L was add to volumetric flask of 100 mL and then diluted to scale line by adding distilled water, thereby the farm wastewater with different concentration was gained. Furthermore, the photocatalytic degradation rates of the farm wastewater were conducted by using Ag/TiO₂ as photocatalyst under simulated sunlight in 180 min where the sample was tested per 30 min, the results were shown in Fig. 6. The farm wastewater with the initial concentration of 0.07 g/L possessed highest degradation rate, which showed that the appropriate concentration of farm wastewater was 0.07 g/L.

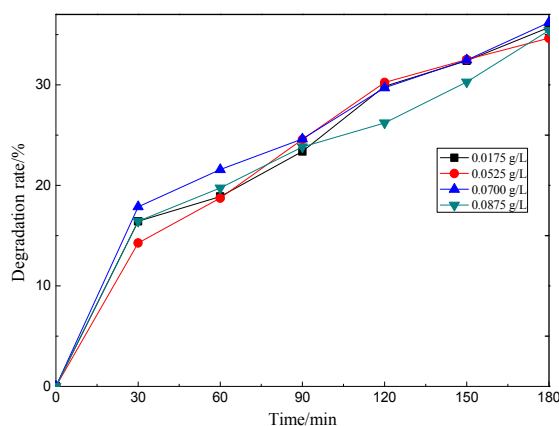


Fig. 6 – The effects of the concentration of farm wastewater on the degradation rate.

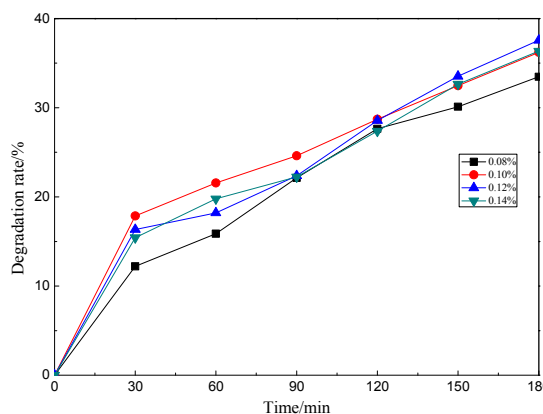


Fig. 7 – The effects of photocatalyst dosage on degradation rate.

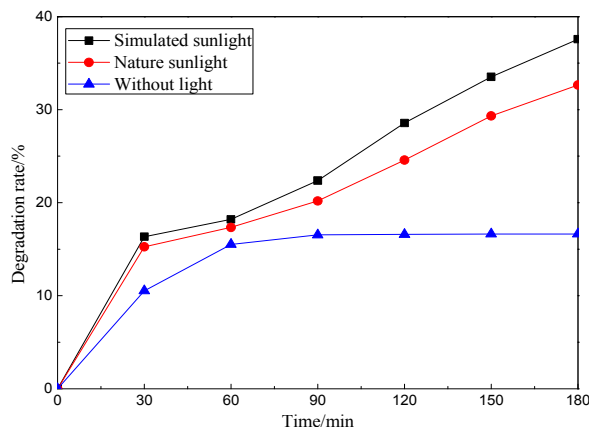


Fig. 8 – Effect of different light on degradation rate of catalyst.

3.3. The effect of amount of catalyst on catalytic property

The influence of amount of photocatalyst on photocatalytic degradation performance of Ag/TiO₂ was also studied by degrading ammonia nitrogen compounds, as seen in Fig. 7. With the extending photocatalytic time, the photocatalytic degradation rate gradually increased. The highest degradation rate reached to 37.5%, as compared with the result of the similar documents, the catalyst showed better catalytic activity.

3.4. The effect of irradiation conditions on the photocatalytic properties of photocatalyst

Furthermore, the irradiation conditions also affected the photocatalytic degradation properties of photocatalyst on ammonia nitrogen compounds,^{11,12} as seen in Fig.8. In comparison with the catalytic degradation rate under different illumination conditions by using Ag/TiO₂ as photocatalyst, the results showed that the degradation rate of ammonia nitrogen compounds was very low without illumination, which might be caused by adsorption. The degradation rate of ammonia nitrogen compounds under simulated sunlight was 37.5%, and under actual sunlight the degradation rate was 32.6%, whereas under without light photocatalyst only indicated adsorption property thereby led to the lowest elimination rate of ammonia nitrogen compounds.

CONCLUSIONS

TiO₂ and transition metal-doping TiO₂ composites were prepared by hydrothermal method. The spectral properties of as-prepared TiO₂ and its composites were studied by means of UV-vis, FTIR, fluorescence spectrometry. The

results showed that transition metal-doping TiO₂ could improve the light response range and decrease the recombined rate of electron-hole, thereby raising the photocatalytic degradation rate of TiO₂ toward ammonia and nitrogen compounds in farm wastewater. The results about photocatalytic degradation properties of TiO₂, Cu/TiO₂, Co/TiO₂, Ni/TiO₂, Ag/TiO₂ and Au/TiO₂ on ammonia-nitrogen compounds in farm wastewater, also displayed that transition metal-doping TiO₂ composites had higher photocatalytic degradation rate than pure TiO₂. Additionally, in comparison with the effect of irradiation conditions on the photocatalytic properties of photocatalyst, it was found that as-fabricated photocatalyst also had perfect photocatalytic degradation performance to ammonia nitrogen compounds under natural light, and degradation rate reached to 32.6% in 180 min, these showed perfect application respect in actual treatment of farm wastewater.

Acknowledgements. This research was financially supported by the Project of Youth Backbone Teachers of Henan Province (Grant No. 2017GGJS172), Henan Provincial Natural Science Foundation of China (Grant Nos. 182102311053 and 192102310492), 2018's Open Program on Key Laboratory of Nanoscale Energy Storage and Conversion Materials of Henan Province in China (Grant No. 2018ISMNM01), and the major science and technology projects of Zhumadian, Henan, China (Grant No. 17702).

REFERENCES

1. X. Chen, S. Shen, L. Guo and S. S. Mao, *Chemical Reviews*, **2010**, *110*, 6503-6570.
2. H. Tong, S. Ouyang, Y. Bi, N. Umezawa, M. Oshikiri and J. Ye, *Advanced Mater.*, **2012**, *24*, 229-251.
3. R. Saravanan, E. Sacari, F. Gracia, M. M. Khan, E. Mosquera and V. K. Gupta, *J. Molecular Liquids*, **2016**, *221*, 1029-1033.
4. L. Liu, L. Ding, Y. Liu, W. J. An, Sh. L. Lin, Y. H. Liang and W. Q. Cui, *Appl. Cat. B: Environ.*, **2017**, *201*, 92-104.

5. S. Wang, L. Pan, J. J. Song, W. B. Mi, J. Zou, L. Wang and X. Zhang, *J. Am. Chem. Soc.*, **2015**, *137*, 2975-2983.
6. K. R. Reddy, K. V. Karthik, S. B. B. Prasad, S. K. Soni, H. M. Jeong and A. V. Raghu, *Polyhedron*, **2016**, *120*, 169-174.
7. R. Su, N. Dimitratos, J. Liu, C. Emma, E. Carter, S. Althahban, X. Q. Wang, Y. B. Shen, S. Wendt, X. D. Wen, J. W. Niemantsverdriet, Bo. B. Iversen, C. J. Kiely, G. J. Hutchings and F. Besenbacher, *Acs. Catalysis*, **2016**, *6*, 4239-4247.
8. J. V. Hernández, S. Coste, A. G. Murillo, F. D. Romo and A. Kassiba, *J. Alloys Comp.*, **2017**, *710*, 355-363.
9. P. Chen, A. Khetan, F. Yang, V. Migunov, P. Weide, S. Sturmer, P. H. Guo, K. Kahler, W. Xia, J. Mayer, H. Pitsch, U. Simon and M. Muhler, *Acs. Catalysis*, **2017**, *7*, 1197-1206.
10. M. M. Momeni, Y. Ghayeb and Z. Ghonchehi, *Ceramics Int.*, **2015**, *41*, 8735-8741.
11. L. Gnanasekaran, R. Hemamalini, R. Saravanan, K. Ravichandran, F. Gracia and V. K. Gupta, *J. Molec. Liquids*, **2016**, *223*, 652-659.
12. X. Zhou, V. Häublein, N. Liu, N. T. Nguyen, E. M. Zolnhofer, H. Tsuchiya, M. S. Killian, K. Meyer, L. Frey and P. Schmuki, *Angewandte Chem. Int. Edition*, **2016**, *55*, 3763-3767.
13. L. L. Tan, W. J. Ong, S. P. Chai and A. R. Mohamed, *Appl. Cat. B: Environ.*, **2015**, *166*, 251-259.
14. G. L. Chiarello, M. H. Aguirre and E. Selli, *J. Catalysis*, **2010**, *273*, 182-190.
15. M. Diak, E. Grabowska and A. Zaleska, *Appl. Surface Sci.*, **2015**, *347*, 275-285.
16. Ministry of Environmental Protection of the People's Republic of China. HJ 535-2009, Water quality-determination of ammonia nitrogen-Nessler's reagent spectrophotometry, 2009.
17. K. Ishibashi, A. Fujishima, T. Watanabe and K. Hashimoto, *J. Photochem. Photobiol. A: Chem.*, **2000**, *134*, 139-142.
18. K. Schute and M. Rose, *Chem. Sus. Chem.*, **2015**, *8*, 3419-3423.